

## Prijava naučnog rada

### Podaci o radu:

Rad <sup>1</sup>	<b>Analysis of Causes of Degradation of Parent Material and Weld Metal of Breeches Pipe nr. 1 of Pipeline III at Hydroelectric Power Plant "Perućica"</b>
ISSN časopisa	<b>1451-3749</b> <b>EISSN 1820-7863</b>
Impakt faktor časopisa <sup>2</sup>	<b>0,21 (SCOPUS)</b>
Datum objavljivanja rada	<b>2015</b>
Naziv liste kojoj časopis pripada	<b>Emerging Sources Citation Index (ESCI)</b> <b>SCOPUS</b>
Ukupan broj autora	<b>5</b>
Broj autora koji nisu zaposleni na UCG	<b>4</b>
Naziv vodećeg autora	<b>Simon Sedmak</b>

### Autori rada:

R.B.	Ime i prezime autora zaposlenih na organizacionoj jedinici
1	Prof.dr Darko Bajić, Mašinski fakultet
2	
3	
4	
5	

Datum podnošenja prijave:

16.03.2018.

Podnosioci prijave:

1. prof.dr Darko Bajić  
(Ime i prezime autora)
2. \_\_\_\_\_  
(Ime i prezime autora)
3. \_\_\_\_\_  
(Ime i prezime autora)
4. \_\_\_\_\_  
(Ime i prezime autora)
5. \_\_\_\_\_  
(Ime i prezime autora)

<sup>1</sup> Puna referenca rada

<sup>2</sup> Ne smije biti stariji od 2015. godine

Naučni časopis Društva za integritet i vek konstrukcija  
The Scientific Journal of the Society for Structural Integrity and Life

---

# Integritet i vek konstrukcija Structural Integrity and Life

ISSN 1451-3749 (štampano izdanje) (printed edition)

EISSN 1820-7863 (Online)



*Jointly published by*



**Society for Structural  
Integrity and Life**

*and*



**IMS Institute**

Editor-in-Chief: **Aleksandar Sedmak**

e-mail: [asedmak@mas.bg.ac.rs](mailto:asedmak@mas.bg.ac.rs)

**Office:** University of Belgrade, Faculty of Mechanical Engineering, Kraljice Marije 16 (room 502), 11000 Belgrade, Serbia

## Editorial Board

Financially supported by the Ministry of Science and Technological Development, Republic of Serbia  
Distributed to members of the Society and to the National Library of Serbia and to the Library of the University of Belgrade

## Publication Ethics and Publication Malpractice Statement

---

## Instructions for Authors

- [Vol. 1, No 1, 2001](#) (only in Serbian, PDF download available)
- [Vol. 1, No 2, 2001](#) (only in Serbian, PDF download available)
- [Vol. 2, No 1-2, 2002](#) (mostly in Serbian, PDF download available)
- [Vol. 3, No 1, 2003](#) (PDF download available)
- [Vol. 3, No 2, 2003](#) (PDF download available)
- [Vol. 4, No 1, 2004](#) (PDF download available)
- [Vol. 4, No 2, 2004](#) (PDF download available)

# INTEGRITET I VEK KONSTRUKCIJA STRUCTURAL INTEGRITY AND LIFE

Vol. 15, No 3, 2015

Sadržaj/Contents ([PDF](#), 154 kB)

**E. Doncheva, B. Medjo, A. Sedmak**

[Analiza parametara otpornosti na lom metodom konačnih elemenata, kod stacionarnih polueliptičnih prslina u čeliku povišene čvrstoće](#)  
[Finite Element Analysis of Fracture Resistance Parameters for Stationary Semi-Elliptical Surface Cracks in High Strength Steel](#)

**T. Pankaj, S.B. Singh, J. Lozanović Šajić**

[Termo-elastoplastična deformacija čvrstog diska sa izvorom toplote opterećenim na pritisak](#)  
[Thermo Elastic-Plastic Deformation in a Solid Disk with Heat Generation Subjected to Pressure](#)

**Ž. Lazarević, I. Arandelović, S. Kirin**

[Analiza slučajnih mašinskih otkaza rotornog bagera](#)  
[An Analysis of Random Mechanical Failures of Bucket Wheel Excavator](#)

**S.A. Sedmak, M. Arsić, D. Bajić, M. Mladenović, Z. Savić, S. Koprivica**

[Analiza uzroka degradacije osnovnog materijala i metala šava račve na hidroelektrani 'Perućica'](#)  
[Analysis of Causes of Degradation of Parent Material and Weld Metal of Breeches Pipe at Hydroelectric Power Plant 'Perućica'](#)

**S. Petronić, M. Burzić, D. Milovanović, K. Čolić, S. Perković**

[Površinska obrada laserom zavarenih nimonik 263 limova](#)  
[Surface Modification of Laser Welded Nimonic 263 Sheets](#)

**A. Saaïdia, A. Bezazi, A. Belbah, S. Amroune, F. Scarpa**

[Procena mehaničkih svojstava prediva konoplje primenom dvo- i tro-parametarskog vejbulovom metoda](#)  
[Evaluation of Mechanical Properties of Jute Yarns by Two- and Three- Parameters Weibull Method](#)

**K. Legweel, A. Sedmak, K. Čolić, Z. Burzić, L. Gubelj**

[Određivanje širine zone konačnog razvlačenja MP35N višefazne legure](#)  
[Final Stretch Zone Width Determination for MP35N Multiphase Alloy](#)

**D. Kalaba, M. Đorđević, V. Ivanović**

[Određivanje funkcija pouzdanosti cevnog sistema kotla u termoelektrani 'nikola tesla, blok A4'](#)  
[Determining the Reliability Functions of the Boiler Tubing System in Power Plant 'Nikola Tesla, Block A4'](#)

**M. Ristić, R. Prokić-Cvetković, B. Katavić, I. Vasović**

[Izbor tehnologija navarivanja usisnih ploča ventilacionog mlina i produžetak njihovog radnog veka](#)  
[Selecting Hardfacing Technologies for Ventilation Mill Suction Plates and Extending its Working Life](#)

**A. Živković, A. Đurđević, A. Sedmak, S. Tadić, I. Jovanović, Đ. Đurđević, K. Zammit**

[Zavarivanje trenjem sa mešanjem aluminijumskih legura – T spojevi](#)  
[Friction Stir Welding of Aluminium Alloys – T Joints](#)

Vesti / News ([PDF](#), 202 kB)

## ANALYSIS OF CAUSES OF DEGRADATION OF PARENT MATERIAL AND WELD METAL OF BREECHES PIPE AT HYDRO POWER PLANT 'PERUĆICA'

## ANALIZA UZROKA DEGRADACIJE OSNOVNOG MATERIJALA I METALA ŠAVA RAČVE NA HIDROELEKTRANI 'PERUĆICA'

Originalni naučni rad / Original scientific paper

UDK /UDC: 620.179:621.643

Rad primljen / Paper received: 05.11.2015

Adresa autora / Author's address:

<sup>1)</sup> University of Belgrade, Innovation Centre of the Faculty of Mechanical Engineering, [simon.sedmak@yahoo.com](mailto:simon.sedmak@yahoo.com)

<sup>2)</sup> Institute for Materials Testing, Belgrade, Serbia

<sup>3)</sup> University of Montenegro, Faculty of Mechanical Engineering, Podgorica, Montenegro

### Keywords

- breeches pipe
- material degradation
- welded joints

### Abstract

*Presented are results of non-destructive tests performed on the parent material and welded joints of structural parts of a breeches pipe (collar and anchor), and results of destructive tests performed on the parent material of the anchor. Non-destructive testing included visual (VT), magnetic particle (MT), and ultrasonic testing (UT), while destructive tests included determination of chemical composition, tensile properties, impact energy and hardness. Based on test results it is established that the major cause for the occurrence of damage in the carrying structure of the breeches pipe no.1 of pipeline III, or in other words, the degradation of anchor parent material and welded joints between the collar and anchor, and between the pipeline and anchor, is in the fact that the breeches pipe started to lean, not on the collar, as specified by design, but on the anchor that could not endure all loads occurring in service.*

### INTRODUCTION

Hydroelectric power plant 'Perućica', which comprises 7 hydroelectric generating sets with an installed power of 330 MW, is the oldest large hydroelectric power plant in Montenegro. It was put into service in 1960. From the accumulations 'Krupac', 'Slano' and 'Vrtac' the water is being brought to the hydroelectric generating set by three pipelines under pressure of 61 bar, /1/. Pipeline I, 1851 m long with diameters 1.8-2.2 m supplies two hydroelectric generating sets (A1 and A2) with nominal power of 38 MW each. Pipeline II, 1883 m long with diameters 2.1-2.2 m supplies three hydroelectric generating sets (A3, A4 and A5) with nominal power of 38 MW each, while pipeline III, 1931 m long with diameters 2.5-2.65 m supplies two hydroelectric generating sets (A6 and A7) with nominal power of 58.5 MW each, Fig. 2. In Fig. 3 the appearance of the Pelton turbine is shown.

The most problematic area of the HPP 'Perućica' is the structure of pipeline III, in the zone of breeches pipe no.1. The pipeline and the breeches pipe are made of micro-alloyed steel Nioval 47 (from steel plant 'Jesenice'). Loads

### Ključne reči

- račva
- degradacija materijala
- zavareni spojevi

### Izvod

*U ovom radu su prikazani rezultati ispitivanja bez razaranja osnovnog materijala i zavarenih spojeva na nosećim delovima račve (kragna i anker), kao i rezultati ispitivanja sa razaranjem osnovnog materijala ankera. Ispitivanje bez razaranja obuhvatalo je vizuelno ispitivanje (VT), ispitivanje magnetnim česticama (MT) i ultrazvučno ispitivanje (UT), dok je ispitivanje sa razaranjem obuhvatalo određivanje hemijskog sastava, zateznih osobina, udarne energije i tvrdoće. Na osnovu rezultata ispitivanja, utvrđen je osnovni uzrok pojave oštećenja na nosećoj konstrukciji račve br. 1 cevovoda III, odnosno, degradacija osnovnog materijala ankera i zavarenih spojeva između kragne i ankera, i između cevovoda i ankera, uz činjenicu da je račva počela da naleže na anker, umesto na kragnu, kao što je bilo predviđeno, usled čega anker nije mogao da nosi svo opterećenje koje se pojavilo tokom rada.*

in that area, which occur during the process of performing in-service functional tasks (stationary and dynamic loads) and during the disturbed process of exploitation (non-stationary dynamic loads), led to the increase of the level of damaging of the parent material and welded joints at the structural parts of the breeches pipe (collars and anchors), which endangers the integrity of the pipeline structure as a whole, Fig. 4. The role of the collar, over which the breeches pipe leans on the foundation, is to receive static and dynamic loads (mean pressure in the pipeline of 61 bar, specific load caused by the quantity of water in the pipeline, effect of gravitational force) and displacements that occur due to non-stationary dynamic loads, while the anchor has the role in strengthening and balancing the mass of the breeches pipe. Significant propagation of the defect at the carrying structure of breeches pipe no.1, mostly at parent material of the anchor and welded joint, between the collar and the anchor, as well as between the pipeline and the anchor, has led to the fact that in 2012 the breeches pipe started to lean not on the collar, but on the anchor, Fig. 5b.

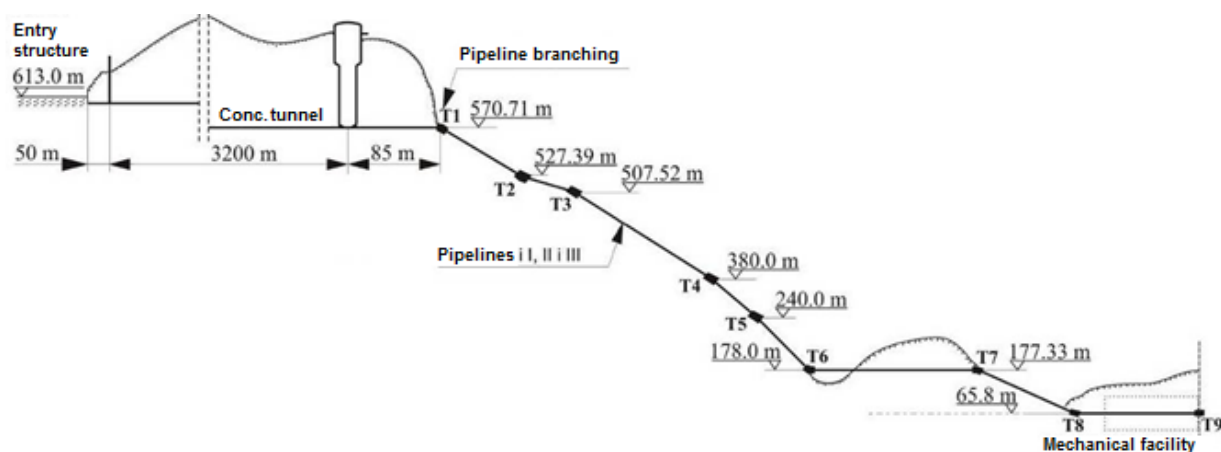


Figure 1. Schematic appearance of hydroelectric power plant 'Perućica'.

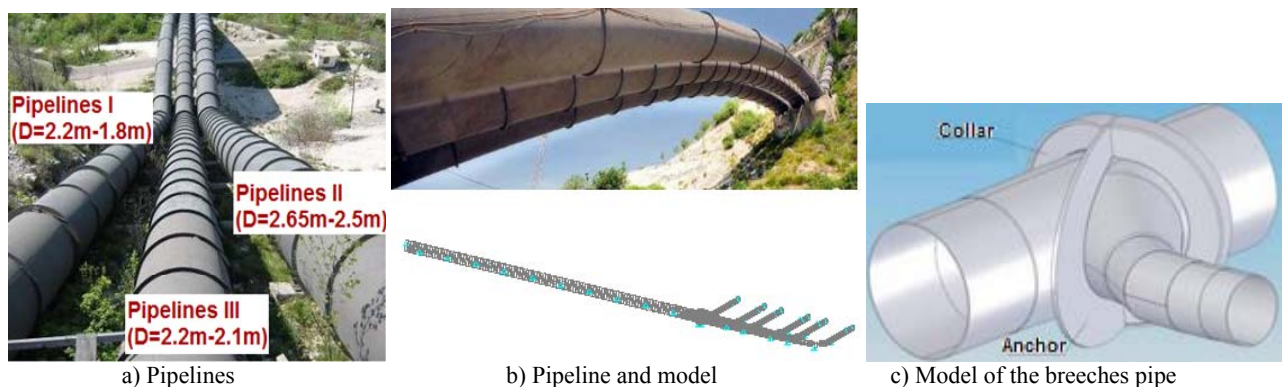


Figure 2. Intake pipelines with suitable models of pipe and breeches pipe.


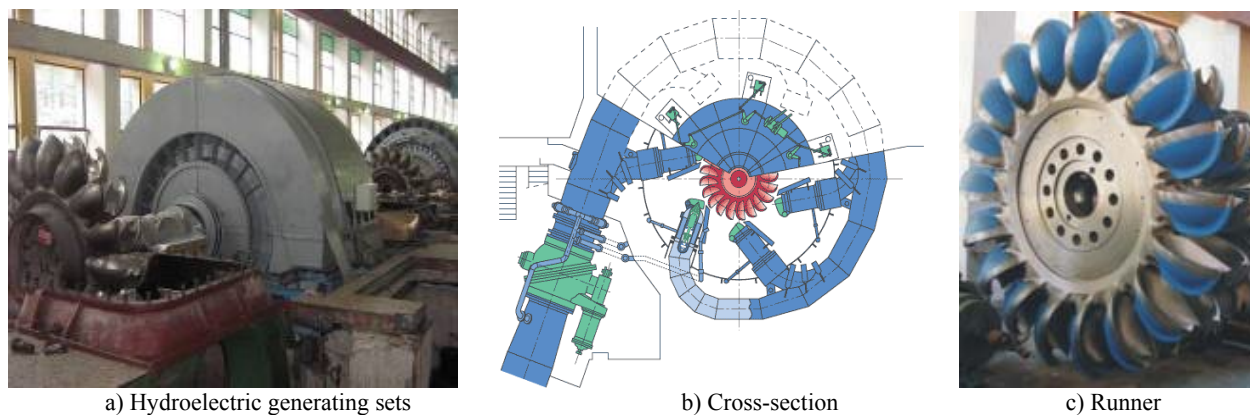


Figure 3. Appearance of a Pelton turbine.



Figure 4. Pipeline III with defects in parent material and welded joints.



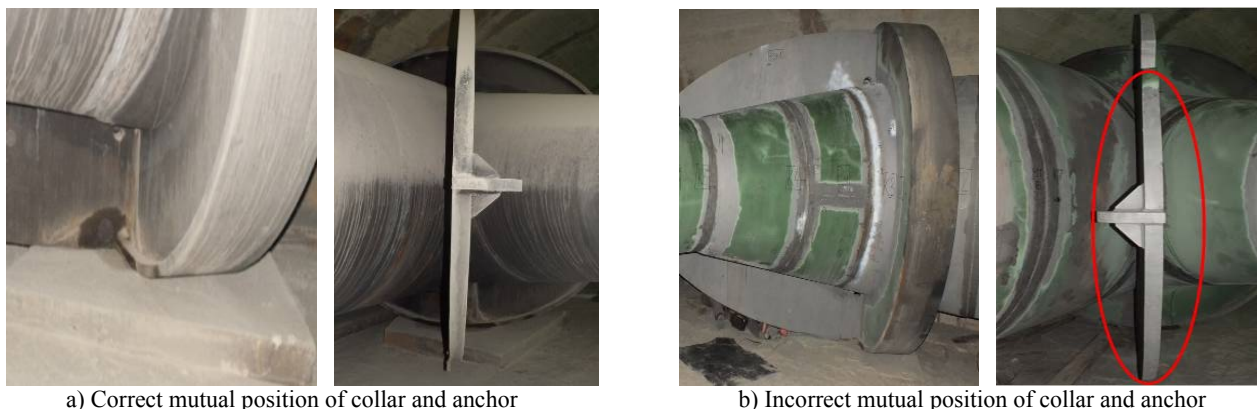

a) Correct mutual position of collar and anchor  
b) Incorrect mutual position of collar and anchor  
Figure 5. Correct mutual position of collar and anchor at breeches pipe and the damage at the anchor caused by bending initiated by incorrect mutual position of collar and anchor (bending of the anchor is shown in Fig. 5b).

## EXPERIMENTAL TESTS

In order to determine the cause of degradation of parent material (PT) and welded joints (WJ) of breeches pipe no.1 at pipeline III, the non-destructive and destructive tests are performed. Non-destructive testing included visual (VT), magnetic particle (MT) and ultrasonic testing (UT), while destructive testing included determination of the chemical composition, tensile properties, impact energy and hardness.


Locations of samples needed for determination of chemical composition, tensile properties, impact energy and hardness are shown in Fig. 6.




Figure 6. Locations of samples for destructive tests.



Figure 7. Cracks at the surface of parent material of the anchor of breeches pipe no.1.

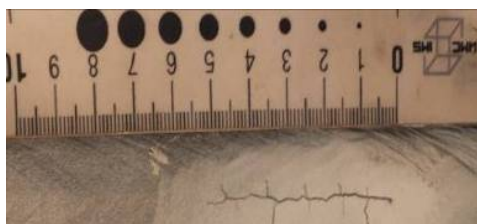

a) Cracks at the surface of WM

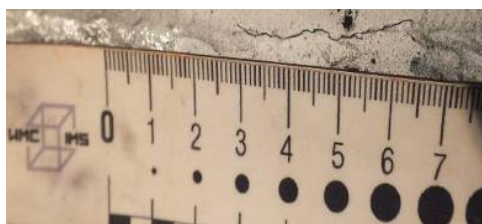

b) Cracks in the HAZ



c) Cracks at the surface of PM

Figure 8. Appearance of cracks detected at parent material and welded joints of breeches pipe no.1.

Tensile and impact energy tests are carried out on specimens from 3 layers and in 3 directions of breeches pipe parent material. Specimens are taken in the direction of sheet metal rolling, perpendicular to the direction of sheet metal rolling, and in the direction of metal sheet thickness.

## RESULTS AND DISCUSSION

### Non-destructive testing methods

Examples of defects detected at parent material (PT), heat-affected zone (HAZ) and weld metal (WM) of the breeches pipe no.1 through visual (VT), /2/, and magnetic particle testing (MT), /3/, are shown in Figs. 7-9. It is determined through ultrasonic testing (UT), /4/, that cracks in parent material presented in Figs. 7 and 8 are 13-32 mm deep, while cracks in the weld metal are 25-52 mm deep.

### Destructive testing methods

Results of quantometric analysis of the chemical composition of the anchor sample of micro-alloyed steel 'Nioval 47' are shown in Table 1 and respond to the chemical composition stated by the steel manufacturer. /1, 5/.

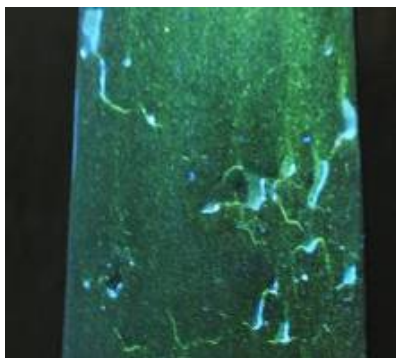


Figure 9. Defects detected in parent material and welded joints of anchor of breeches pipe no.1.

Table 1. Chemical composition results.

Steel	Chemical composition (mass %)						
	C	Si	Mn	P	S	Cr	Ni
	0.17	0.41	1.48	0.012	0.002	0.12	0.09
	Cu	Mo	V	Sn	Nb	Al	
	0.21	0.02	0.07	0.007	0.045	0.061	

From the delivered sample of anchor material 3, standard specimens are extracted in 3 mutually perpendicular directions for tensile testing. Diameter of the measurement area is 8 mm, which is in accordance with the standard /6/. Testing is performed on the machine for tensile, compression, and bend testing, produced by A.J. Amsler, from Switzerland, with a maximal measurement range of 98.1 kN. Test results shown in Table 2 do not deviate from those stated by the manufacturer of microalloyed steel Nioval 47.

Results of standard hardness testing performed on the surface and along the cross-section of polished plates extracted from adequate samples in accordance with the standard, /7/, are presented in Table 3. On the basis of obtained results it can be concluded that they do not deviate significantly from those prescribed by the steel manufacturer.

Table 2. Tensile test results, obtained at 20°C, in accordance with SRPS EN 10002-1.

Sample position	Specimen	Yield strength $R_e$ (N/mm <sup>2</sup> )	Tensile strength $R_m$ (N/mm <sup>2</sup> )	Elongation $A_{5.65}$ (%)	Contraction Z (%)
Direction of rolling	Surface layer	507	643	30.00	65.48
	Middle layer	516	650	26.50	59.36
	Lower layer	503	643	27.00	60.94
Perpendicular to the direction of rolling	Surface layer	486	630	25.75	66.94
	Middle layer	511	648	27.50	60.94
	Lower layer	487	622	22.50	65.48
z-direction	Surface layer	463	506	6.67	12.89
	Middle layer	469	640	14.00	24.88
	Lower layer	-	147	-	-

Table 3. Results of hardness testing, SRPS ISO 6506-1.

Measurement position	Hardness (HBW 5/750/20°)	Mean value (HB)
On the surface	217, 219, 217	218
Along the cross-section	211, 193, 202	202

Table 4. Impact energy test results, SRPS EN 10045-1.

Sampling position	Specimen	Temperature T (°C)	Impact energy KV <sub>2/300</sub> (J)	Mean value (J/cm <sup>2</sup> )
Direction of rolling	1	+20	120.66	104.97
	2		112.82	
	3		81.42	
Perpendicular to rolling direction	1	+20	139.30	126.55
	2		130.47	
	3		109.87	
z-direction	1	+20	31.39	25.50
	2		21.58	
	3		23.54	

Impact energy tests are performed by Charpy pendulum 'Alfred Amsler', with range of 0-300 J, using V2-notch specimens with dimensions of 10×10×55 mm taken from 3 mutually perpendicular directions of the sample, in accordance with the standard /8/. Test results presented in Table 4 are satisfactory.

## CONCLUSION

Test results show that the major cause for damage occurrence in the load carrying structure of breeches pipe no.1 of pipeline III at hydroelectric power plant 'Perućica', or in other words of the parent material degradation in the anchor and welded joints placed between the collar and the anchor, and between the pipeline and anchor, is that the breeches pipe started to lean not on the collar, as defined by the project, but on the anchor which could not endure all loads that occur during service.

## ACKNOWLEDGEMENT

Authors wish to thank the Ministry of Education, Science and Technological Development of Serbia for supporting the paper as part of the EVB project: 35002-TR.

## REFERENCES

1. Documentation of pipeline manufacturer, Steel mill 'Jesenice', Slovenia, 1960.
2. SRPS EN 970: NDT - Non-destructive examination of fusion welds. Visual examination, 2003.
3. SRPS EN 17638: Non-destructive testing of welds. Magnetic particle testing, 2012.
4. SRPS EN 1714: Non-destructive testing of welded joints. Ultrasonic testing of welded joints, 2010.
5. Bakić, R., Milović, Lj., Jovičić, R., Sedmak, S., *Quality Assurance of Storage Tanks after In-Service Crack Repairs*, Structural Integrity and Life (Integritet i vek konstrukcija), 13 (1): 63-74, 2013.
6. SRPS EN 6892-1 (substituted SRPS EN 10002-1:1996): Metallic materials - Tensile testing - Part 1: Method of test at room temperature, 2012.
7. SRPS ISO 6506-1: Metallic materials - Brinell hardness test - Part 1: Test method, 2011.
8. SRPS EN ISO 148-1 (substituted SRPS EN 10045-1:1993): Metallic materials - Charpy pendulum impact test - Part 1: Test method, 2012.

## VHCF7 – SEVENTH INTERNATIONAL CONFERENCE ON VERY HIGH CYCLE FATIGUE Dresden, Germany, 3-5 July 2017

Aims and Scope

With an increasing scarcity of resources, strategies to realize the most efficient design and engineering of components and hence an optimum utilization of cyclic strength of engineering materials becomes more and more important. Nowadays a growing number of components have to withstand a number of loading cycles well beyond the classical fatigue limit. Thus, there is a global interest in, and need for, an improved understanding of the fatigue behavior of structural materials in the very high cycle fatigue range in order to develop reliable fatigue life prediction methods for number of cycles of 10<sup>6</sup> to 10<sup>10</sup> or even higher. VHCF7 will continue the tradition to serve as a lively and fertile platform bringing together the international VHCF community and all those interested to present, discuss and learn about the latest findings from fundamental and applied research and to get to know the impact on practical applications.

The conference will comprise invited keynote lectures by outstanding international scientists, contributed oral presentations and posters. Suggestions for special topics are welcome. The conference language is English and the contributions are planned to be published via a renowned reviewed open-access journal.

VHCF History/Chairs

- VHCF1 Paris, France, 1998  
*C. Bathias*
- VHCF2 Vienna, Austria, 2001  
*S. Stanzl-Tschegg, H. Mayer*
- VHCF3 Kyoto/Kusatsu, Japan, 2004  
*T. Sakai, Y. Ochi*
- VHCF4 Ann Arbor, USA, 2007  
*J.E. Allison, J.W. Jones, J.M. Larsen, R.O. Ritchie*
- VHCF5 Berlin, Germany, 2011  
*C. Berger, H.-J. Christ*
- VHCF6 Chengdu, China, 2014  
*Q.Y. Wang, Y.S. Hong*

Chairs

- *Prof. Dr.-Ing. Martina Zimmermann*  
Institut für Werkstoffwissenschaft, TU Dresden and  
Fraunhofer Institut für Werkstoff- und Strahltechnik  
Dresden, Germany  
[martina.zimmermann@iws.fraunhofer.de](mailto:martina.zimmermann@iws.fraunhofer.de)
- *Prof. Dr.-Ing. habil. Hans-Jürgen Christ*  
Institut für Werkstofftechnik, Universität Siegen  
Siegen, Germany  
[hans-juergen.christ@uni-siegen.de](mailto:hans-juergen.christ@uni-siegen.de)

Organizer

German Association for  
Materials Research and Testing e.V.

Gutshaus Schloßstraße 48 | 12165 Berlin I Germany  
Phone: +49 30 8113066 | Fax: +49 30 8119359  
[office@dvm-berlin.de](mailto:office@dvm-berlin.de) | [www.dvm-berlin.de](http://www.dvm-berlin.de)

Timelines

Spring 2016 – Call for Papers  
Autumn 2016 – Early Bird Registration Opening  
early 2017 – Deadline for Manuscript Submission  
May 2017 – Final Programme

Language

The conference language is English and will be required for abstracts, papers, posters and oral contributions.



Semperoper, Dresden



- [Support](#)
- [Training](#)
- [Contact Us](#)
- [clarivate.com](#)

[Master Journal List](#)

Site

Client

proxystylesheet

Output

Search  

allAreas

## Journal Search

### Emerging Sources Citation Index - JOURNAL LIST

[A](#) [B](#) [C](#) [D](#) [E](#) [F](#) [G](#) [H](#) [I](#) [J](#) [K](#) [L](#) [M](#) [N](#) [O](#) [P](#) [Q](#) [R](#) [S](#) [T](#) [U](#) [V](#) [W](#) [X](#) [Y](#) [Z](#)

Total journals: **406** · "S" Journals 311-320 (of 406)



Format for print A-Z

- **STRATEGIC MANAGEMENT**

Quarterly ISSN: 1821-3448

UNIV NOVI SAD, FAC ECONOMICS SUBOTICA, SEGEDINSKI PUT 9-11, SUBOTICA, SERBIA, 24000

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRATEGIC REVIEW FOR SOUTHERN AFRICA**

Semiannual ISSN: 1013-1108

UNIV PRETORIA, INST STRATEGIC STUDIES, C/O EDITOR, STRATEGIC REVIEW SOUTHERN AFRICA, PRETORIA, SOUTH AFRICA, 0002

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRATEGIES FOR POLICY IN SCIENCE AND EDUCATION-STRATEGII NA OBRAZOVATELNATA I NAUCHNATA POLITIKA**

Bimonthly ISSN: 1310-0270

NATL IZDATELSTVO AZ BUKI, BUL TSARIGRADSKO SHOSE, 125, BL 5, SOFIA, BULGARIA, 1113

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRATEGIES IN TRAUMA AND LIMB RECONSTRUCTION**

Tri-annual ISSN: 1828-8928

SPRINGER HEIDELBERG, TIERGARTENSTRASSE 17, HEIDELBERG, GERMANY, D-69121

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRENAE-RECHERCHES SUR LES LIVRES ET LES OBJETS CULTURELS DE L'ENFANCE**

Annual ISSN: 2109-9081

UNIV FRANCOIS-RABELAIS, STRENAE, DEPT FRANCAIS EQUIPE INTRU, CECILE BOULAIRE, 3, RUE TANNEURS, BP 4103, TOURS CEDEX 1, FRANCE, 37041

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRENGTH FRACTURE AND COMPLEXITY**

Quarterly ISSN: 1567-2069

IOS PRESS, NIEUWE HEMWEG 6B, AMSTERDAM, NETHERLANDS, 1013 BG

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STROKE RESEARCH AND TREATMENT**

ISSN: 2090-8105

HINDAWI LTD, ADAM HOUSE, 3RD FLR, 1 FITZROY SQ, LONDON, ENGLAND, W1T 5HF

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRUCTURAL INTEGRITY AND LIFE-INTEGRITET I VEK KONSTRUKCIJA**

Tri-annual ISSN: 1451-3749

SOC STRUCTURAL INTEGRITY & LIFE, INST ISPITVANJE MATERIJALA, BULEVAR VOJVODE MISICA 43, BELGRADE, SERBIA, 00000

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRUCTURAL MONITORING AND MAINTENANCE**

Quarterly ISSN: 2288-6605

TECHNO-PRESS, PO BOX 33, YUSEONG, DAEJEON, SOUTH KOREA, 305-600

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **STRUCTURES**

Quarterly ISSN: 2352-0124

ELSEVIER SCIENCE INC, 360 PARK AVE SOUTH, NEW YORK, USA, NY, 10010-1710

[Coverage](#)

- [Emerging Sources Citation Index](#)

---

Total journals: **406** · "S" Journals 311-320 (of 406)



Format for print A-Z

CiteScore metrics for serials

CiteScore metrics from Scopus are comprehensive, transparent, current and free metrics for serial titles in Scopus. Search or browse below to find a source and see associated metrics. Use the annual metrics for reporting, and track the progress of 2017 metrics with CiteScore Tracker 2017. Be sure to use qualitative as well as the below quantitative inputs when presenting your research impact, and always use more than one metric for the quantitative part.

Documents from 3 years

Citations in 2016

201220132014201520162017

Search for a source

Browse sources

Download Scopus Source List

Search

STRUCTURAL INTEGRITY AND LIFE

X

Q

☐ Title

☐ ISSN

☐ Publisher

☐ Display only Open Access journals

i

1 source found matching "STRUCTURAL INTEGRITY AND LIFE".

Clear filters

Source title

CiteScore

SJR

SNIP

Type

Structural Integrity and Life Open Access

0.21

0.132

0.160

Journal

Top of page

About Scopus

- What is Scopus
- Content coverage
- Scopus blog
- Scopus API
- Privacy matters

Language

- 日本語に切り替える
- 切换到简体中文
- 切换到繁体中文
- Русский язык

Customer Service

- Help
- Contact us

Structural Integrity and Life

Open Access ⓘ

Scopus coverage years: 2010, from 2015 to 2017

Publisher: Society for Structural Integrity and Life

ISSN: 1451-3749 E-ISSN: 1820-7863

Subject area: [Engineering: Safety, Risk, Reliability and Quality](#) [Materials Science: Metals and Alloys](#)  
[Engineering: Civil and Structural Engineering](#) [Engineering: Mechanics of Materials](#)

[View all documents](#) >

[Set document alert](#)

[Journal Homepage](#)

[Visit Scopus Journal Metrics](#) ↗

CiteScore 2016 ⓘ  
**0.21**

SJR 2016 ⓘ  
**0.132**

SNIP 2016 ⓘ  
**0.160**

[CiteScore](#) [CiteScore rank & trend](#) [Scopus content coverage](#)

CiteScore 2016

Calculated using data from **31 May, 2017**

**0.21** =  $\frac{\text{Citation Count 2016}}{\text{Documents 2013 - 2015}^*}$  =  $\frac{6 \text{ Citations} >}{29 \text{ Documents} >}$

\*CiteScore includes all available document types

[View CiteScore methodology](#) >

[CiteScore FAQ](#) >

CiteScoreTracker 2017 ⓘ

Last updated on *06 March, 2018*  
Updated monthly

**0.67** =  $\frac{\text{Citation Count 2017}}{\text{Documents 2014 - 2016}}$  =  $\frac{39 \text{ Citations to date} >}{58 \text{ Documents to date} >}$

Metrics displaying this icon are compiled according to Snowball Metrics ↗, a collaboration between industry and academia.

CiteScore rank ⓘ

Category	Rank	Percentile
Engineering		
└ Safety, Risk, Reliability and Quality	#105/135	21st
Materials Science		
└ Metals and Alloys	#108/136	20th
Engineering		

[View CiteScore trends](#) >

[Add CiteScore to your site](#) ↗

About Scopus

- [What is Scopus](#)
- [Content coverage](#)
- [Scopus blog](#)
- [Scopus API](#)
- [Privacy matters](#)

Language

- [日本語に切り替える](#)
- [切换到简体中文](#)
- [切换到繁體中文](#)
- [Русский язык](#)

Customer Service

- [Help](#)
- [Contact us](#)



Link Rada:

<http://divk.inovacionicentar.rs/ivk/ivk15/147-IVK3-2015-SAS-MA-DB-MM-ZS.pdf>